

STRENGTHENING OF REINFORCED CONCRETE BEAMS WITH CARBON FIBER REINFORCED POLYMERS

Ayman G. Abdel-Rahman and Faiz A. Mirza

Civil Engineering Department, College of Engineering and Islamic Architecture
Umm Al-Qura University, P.O. Box 6298, Makkah, Saudi Arabia

ABSTRACT

Strengthening of structures is a complex task. Different systems can be used in order to utilize the fiber reinforced polymer in the most efficient way. Two techniques for surface reinforcement in reinforced concrete beams are addressed in this paper, namely, externally bonded laminates (EBL) and near surface mounted strips (NSM). The experimental work involves seven full-scale reinforced concrete beams strengthened with carbon fiber reinforced polymers (CFRP) and tested up to failure to illustrate two methods of field application and construction techniques of strengthening. The performance and effectiveness of these techniques are demonstrated by comparing the test results of both strengthened and un-strengthened beams. Test results indicate that both techniques are effective in increasing the flexural capacity of R.C. beams. Also it was observed that the beams strengthened with NSM reinforcements show different failure modes than the externally bonded FRP. Applications of the two methods of strengthening R.C beams are suitable for all cases, but prior to the installation of surface bonded CFRP reinforcement, attention should be directed toward investigating the surface concrete on which the composites are to be bonded.

تعتبر تقوية المنشآت باستخدام ألواح البوليمرات المسلحة بألياف الكربون من أكثر الطرق فاعلية في تقوية المنشآت. في هذا البحث تم استخدام طريقتين مختلفتين لتقوية الكمرات المسلحة: في الطريقة الأولى (EBL) تم لصق هذه الألواح مباشرة على السطح السفلي للكمرة. وفي الطريقة الثانية (NSM) تم زرع هذه الألواح قريبة من السطح. وقد أجريت التجارب المعملية على عدد 7 كمرات لدراسة سلوكها بعد تقويتها بهاتين الطريقتين حيث تم تحميل هذه الكمرات بعد إجراء التقوية حتى الكسر و تم تحديد العلاقة بين الحمل المؤثر و الترخيم المقابل وكذلك تم تحديد حمل الكسر لكل الكمرات. وقد اتضح من النتائج فعالية كل من الطريقتين في زيادة قدرة تحمل الكمرات المقواة بألياف الكربون عن مثيلاتها التي لم يتم تقويتها وقد أظهرت النتائج أن الطريقة الثانية أكثر فعالية في تقوية المنشآت من حيث زيادة قدرة التحمل للكمرات وكذلك كمية الألواح المستخدمة في عملية التقوية حيث يتم استخدام كمية أقل عن المستخدمة في الطريقة الأولى.

Keywords: Flexural Strengthening; Carbon Fiber Reinforced Polymers; Externally Bonded Laminates; Near Surface Mounted Strips; Modes of Failure.

1. INTRODUCTION

Fiber-reinforced polymer "FRP" reinforcement became very attractive in the field of reinforced concrete structures both for new constructions strengthening or upgrading of existing structures. The success of the composite reinforcement is mainly linked to their high mechanical performances, low weight, satisfactory durability in an aggressive environment. Several applications for FRP reinforcements have been made all over the world and an increasing market with a high variety of reinforcement is registered at present, [1].

Science 1982, externally bonded (EB) FRP sheet / strip has been successfully applied to strengthen concrete structures, [2]. Although externally bonded FRP reinforcement performed externally well in practice, premature debonding failure was observed and identified by many researches [3,4,5]. Several details were proposed to avoid this type of failure,

which is unacceptable from the point of view of structural safety, [6,7].

Near surface mounting (NSM) FRP technique has many advantages compared with the externally bonding (EB) technique; larger bond surface induces better anchorage capacity, provides higher resistance against peeling-off, a higher percentage of the tensile strength can be mobilized, and no preparation work is needed other than grooving, therefore reduced installation time will be required, [8]. FRP reinforcement due the special mounting setup is protected against mechanical by the surrounding concrete influence, therefore, this technique is attractive for strengthening in the negative moment region. The strengthening has an improved protection against freeze/thaw cycles, elevated temperature, fire, ultraviolet rays and vandalism, [9,10,11].

A series of R.C beams strengthened with near surface mounted (NSM) CFRP strips were tested up to

failure. Test results demonstrated the effectiveness of this technique compared with the externally bonded technique. The results showed a substantial increase in cracking and failure loads for strengthened specimens. The experiments showed also improvement in ductility, preferable composite action, and an ultimate load development more independent from concrete tensile strength, [12,13,14].

Now there is a great potential in FRP strengthening, however, it is important to have sufficient knowledge on the behavior and applicability of different FRP materials and techniques. This paper presents an experimental investigation to evaluate the performance and effectiveness of both externally bonded laminates and near surface mounted strips techniques by comparing the test results of strengthened and the unstrengthened beams.

2. EXPERIMENTAL WORK

This experimental work is carried out in order to evaluate the effect of Externally Bonded(EB), as well as Near Surface Mounted(NSM), Carbon Fiber Reinforced Polymers (CFRP) on the flexural behavior of reinforced concrete beams.

A total of seven full scale simply supported rectangular beams are tested. All the seven beams had clear span length 2.80 m (beams were 3 m long) and cross-section dimensions of 20 x 50cm. These beams had an internal reinforcement provided by top reinforcement consisted of two 10mm in diameter steel bars, and a bottom reinforcement consisted of

three 16 mm in diameter steel rebars running along the full length of the beam. Shear reinforcement consisted of double-legged steel stirrups (8 mm in diameter), uniformly spaced at 125mm, as shown in Fig. 1.

One beam (beam B1) was tested as a control specimen, while three other beams (B2, B3, B4) were strengthened with one, two, and three adjacent strips of externally bonded CFRP reinforcement respectively. The other three beams (B5, B6, B7) were strengthened using one, two, and three CFRP strips of near surface mounted CFRP inserted into grooves cut at the bottom surface of the beams.

2.1 Materials

The characteristics of the materials used in the present work are described in the following:

1. Concrete of compressive strength 35 MPa was used in the present work. The beams were reinforced by high grade steel with yield strength of 400 MPa and an ultimate strength of 600 MPa.
2. Composite material CFRP has been used in this experimental work, named "CarboDur" which is a pultruded carbon fiber reinforced polymers laminates designed for strengthening of concrete structures. Sika CarboDur was bonded to the RC beams as an external reinforcement using an epoxy resin conforms to the current ASTM C-881 and AASHTO M-235 specifications. The properties of CFRP laminates are reported in Table 1.

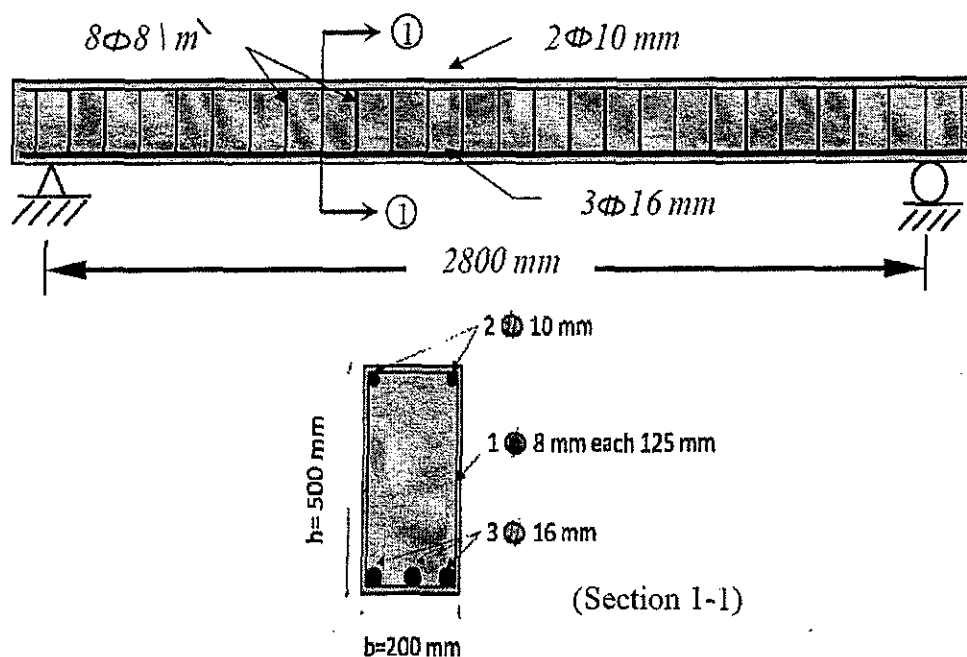


Fig. 1: Beam details

Table 1: Properties of CFRP laminates.

Base	CFRP with an epoxy resin matrix
Color	Black
Tensile strength	2800 MPa (168 kN)
Modulus of Elasticity	160,000 Mpa
Elongation at break	1.69%
Design strain	0.85%
Thickness	1.2 mm
Width	50 mm
Gross sectional Area	60 mm ²
Temperature resistance	> 150°C
Fiber volumetric content	68%
Density	1.60 gm/cm ³
Ultimate strain	1.996

2.2 SPECIMENS PREPARATION AND STRENGTHENING

All tested beams were cast in wooden forms of dimensions 20 x 50 x 300 cm using ready-mix concrete of 35 MPa. After one day, the wooden forms were de-molded and all beams were cured by tap water for seven days and tested after about one month.

2.3 Strengthening with externally bonded CFRP

1. Surface preparation:

The concrete surface was grinded to a concrete surface profile (CSP) 3, as defined by the International Concrete Research Institute (ICRI). Then the surface was cleaned carefully. After that, large holes and irregularities on the surface were filled with putty.

2. Application of the resin & CFRP:

Epoxy paste was prepared by mixing its components in certain proportions. During its pot life, the paste was applied to the surface of beams with a spatula to a minimum thickness 1.5mm. At the same time, the epoxy paste was applied on the CFRP laminates by the same thickness (1.5mm). The CFRP laminates were then placed on the concrete surface within the pot life of the epoxy paste (each of 50 mm width as shown in Fig. 2). Then the laminates were pressed into the epoxy resin until the adhesive was forced out on both sides using a hard rubber roller. The excess adhesive was then removed. Wrapping anchorage using FRP sheets was applied only for a length of 20 cm apart of the support of beams strengthened with externally bonded CFRP (B2, B3, and B4) to eliminate the possibility of failure as a result of splitting of the externally bonded CFRP. The above mentioned procedure for the strengthening of the beams with CFRP laminated is shown in Fig. 2.

2.4 Strengthening with near surface mounted CFRP

The strips, as provided by the manufacturer, have a nominal width of 50mm and a total thickness of 1.2mm. In order to insert the strip within a typical concrete cover used for concrete members, the strips were cut into two halves each 25mm wide. Using a concrete saw, approximately 5mm wide and 25mm deep grooves were cut into the bottom surface of the beams. The grooves were injected with epoxy adhesive to provide the necessary bond with the surrounding concrete. The strips were carefully placed into the grooves to ensure that they were completely covered with epoxy. Strengthening beams by the NSM strips is illustrated in Fig. 3.

2.5 Test Set-up and Instrumentation

The beams were tested under two point loads applied at one meter span. The vertical deflections at mid-span and the strains in concrete and steel were measured using strain gauges.

The deflectometer used to measure the vertical deflection at mid-span is located at point (1), the strain gauge used to measure tensile strain in steel is positioned at point (2), while compressive strains in concrete was measured by two strain gauges located at points (3, 4), finally the tensile strains in the composite materials are measured using strain gauges installed at mid-span at point (5). The distribution and location of the strain gauges used are shown in Fig. 4.

The beams were tested under open steel frame with a maximum capacity of 1000 KN. The load was applied in an increment of 20 KN, and the corresponding deflections and strains were reported. All beams were painted by plastic white paint to observe the crack generation and propagation (map cracking).

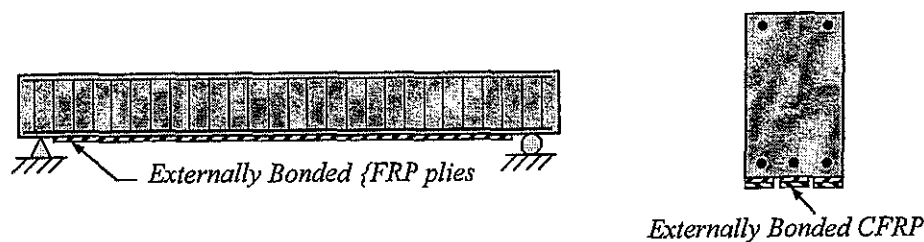


Fig. 2: Strengthening with externally bonded CFRP

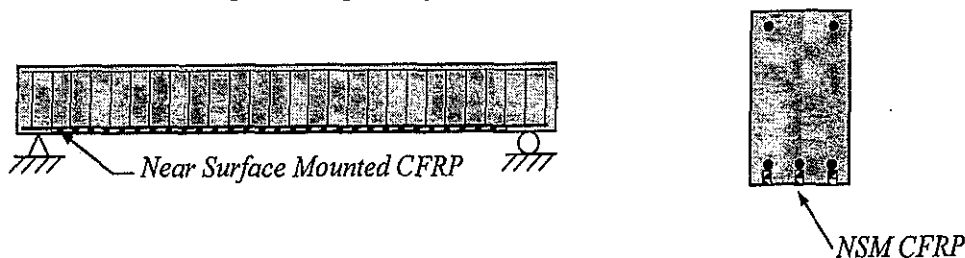


Fig. 3: Strengthening with NSM CFRP.

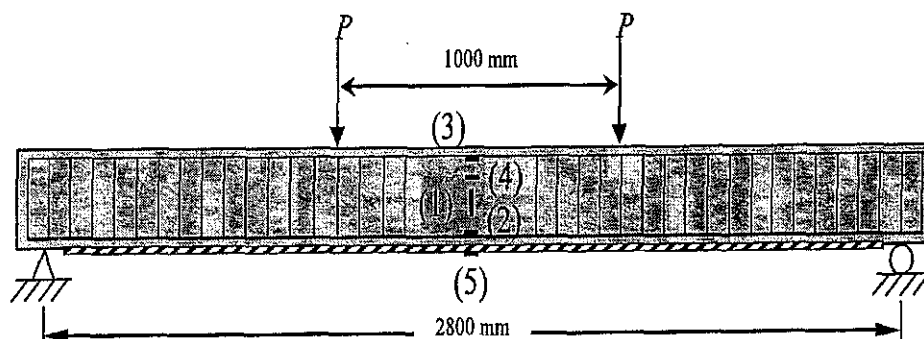


Fig. 4: Test set-up and location of the strain gauges

3. RESULTS AND DISCUSSIONS

The present work investigated the effect of using two strengthening techniques; the first one was externally bonded CFRP, while the second technique was the near surface mounted CFRP reinforcements, on the flexural behavior of reinforced concrete beams.

A total of seven simply supported rectangular beams were tested up to failure. The flexural behavior was investigated in terms of flexure capacity, load-deflection relationships, strains induced in concrete and steel reinforcements, and modes of failure of the tested beams. The performance and effectiveness of the two strengthening techniques were demonstrated by comparing the test results of the strengthened and the un-strengthened beams. Test results are summarized in Table 3. Curves were plotted to explain the behavior of tested beams under static load up to failure.

In general, the control beam developed flexural tensile cracks in the constant moment regions at load of 100 kN. At loads near 300 kN, the tensile reinforcing steel yielded. Finally, the beam failed in compression due to crushing of extreme compression

concrete fibers at load of 340 kN (compression failure).

All beams strengthened with Externally Bonded CFRP as well as NSM CFRP showed significant increases in flexural stiffness and ultimate capacity as compared with the control beam.

3.1 Flexural behavior of beams strengthened by externally bonded (EB) CFRP

Beams strengthened with one, two, and three externally bonded CFRP (B2, B3, and B4) had an increase in the ultimate load by 31%, 60%, and 89% respectively over the control beam (B1) as shown in Table 2. The measured mid-span deflection of the EB strengthened beams were 26.5mm, 24mm, and 22mm respectively, while the mid-span deflection value for the control beam was 28mm. The relationship between mid-span deflections and the applied load up to failure for beams strengthened with EB CFRP laminates is illustrated in Fig. 5. From this figure, similar behavior for all beams could be observed except that as the number of strips increased the load at which the first crack occurred is increased too.

